


## Fomblin Y™ (FOM)

	C 1s					O 1s	F 1s
	1	2	3	4	5		
BE (eV)	291.40	293.23	293.80	294.09	295.19	535.71	689.08
FWHM (eV)	0.98	0.86	0.81	0.98	1.38	1.26	1.54
Area (%)	30	30	30	7	4		
A	0.14	0.00	0.09	0.07	0.03	0.11	0.10
m	1.00	0.96	0.96	0.96	0.96	0.84	0.81

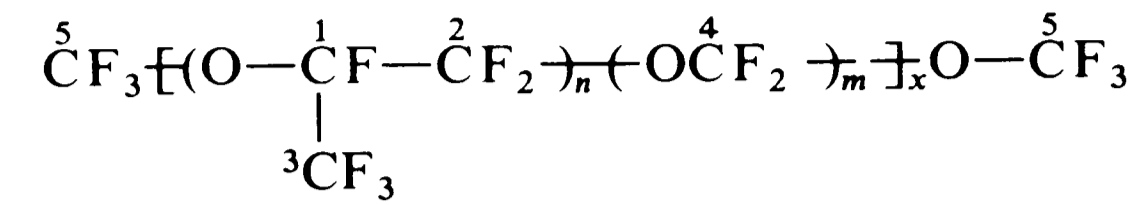

Source: Montedison USA, Inc.  
 Casting solution: (oil, smeared over glass disc)  
 Degradation index: not measured.  
 VB acquisition: 1  
 Charging reference: see comment

Comments: BE of C-1 = 291.40 eV [S. Noel, L. Boyer and C. Bodin, *J. Vac. Sci. Technol. A*, **9**, 32 (1991)]

