

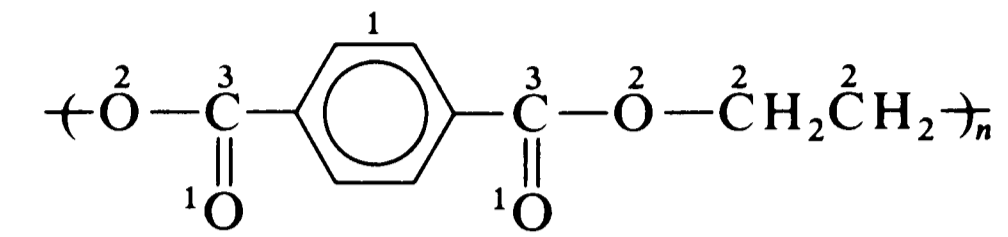


Poly(ethylene terephthalate) (PET)

	C 1s			O 1s	
	1	2	3	1	2
<i>BE</i> (eV)	284.70	286.24	288.66	531.62	533.22
<i>FWHM</i> (eV)	0.99	1.09	0.85	1.19	1.31
Area (%)	59	22	19	47	53
<i>A</i>	0.13	0.13	0.14	0.13	0.09
<i>m</i>	0.89	0.82	0.95	0.84	0.84

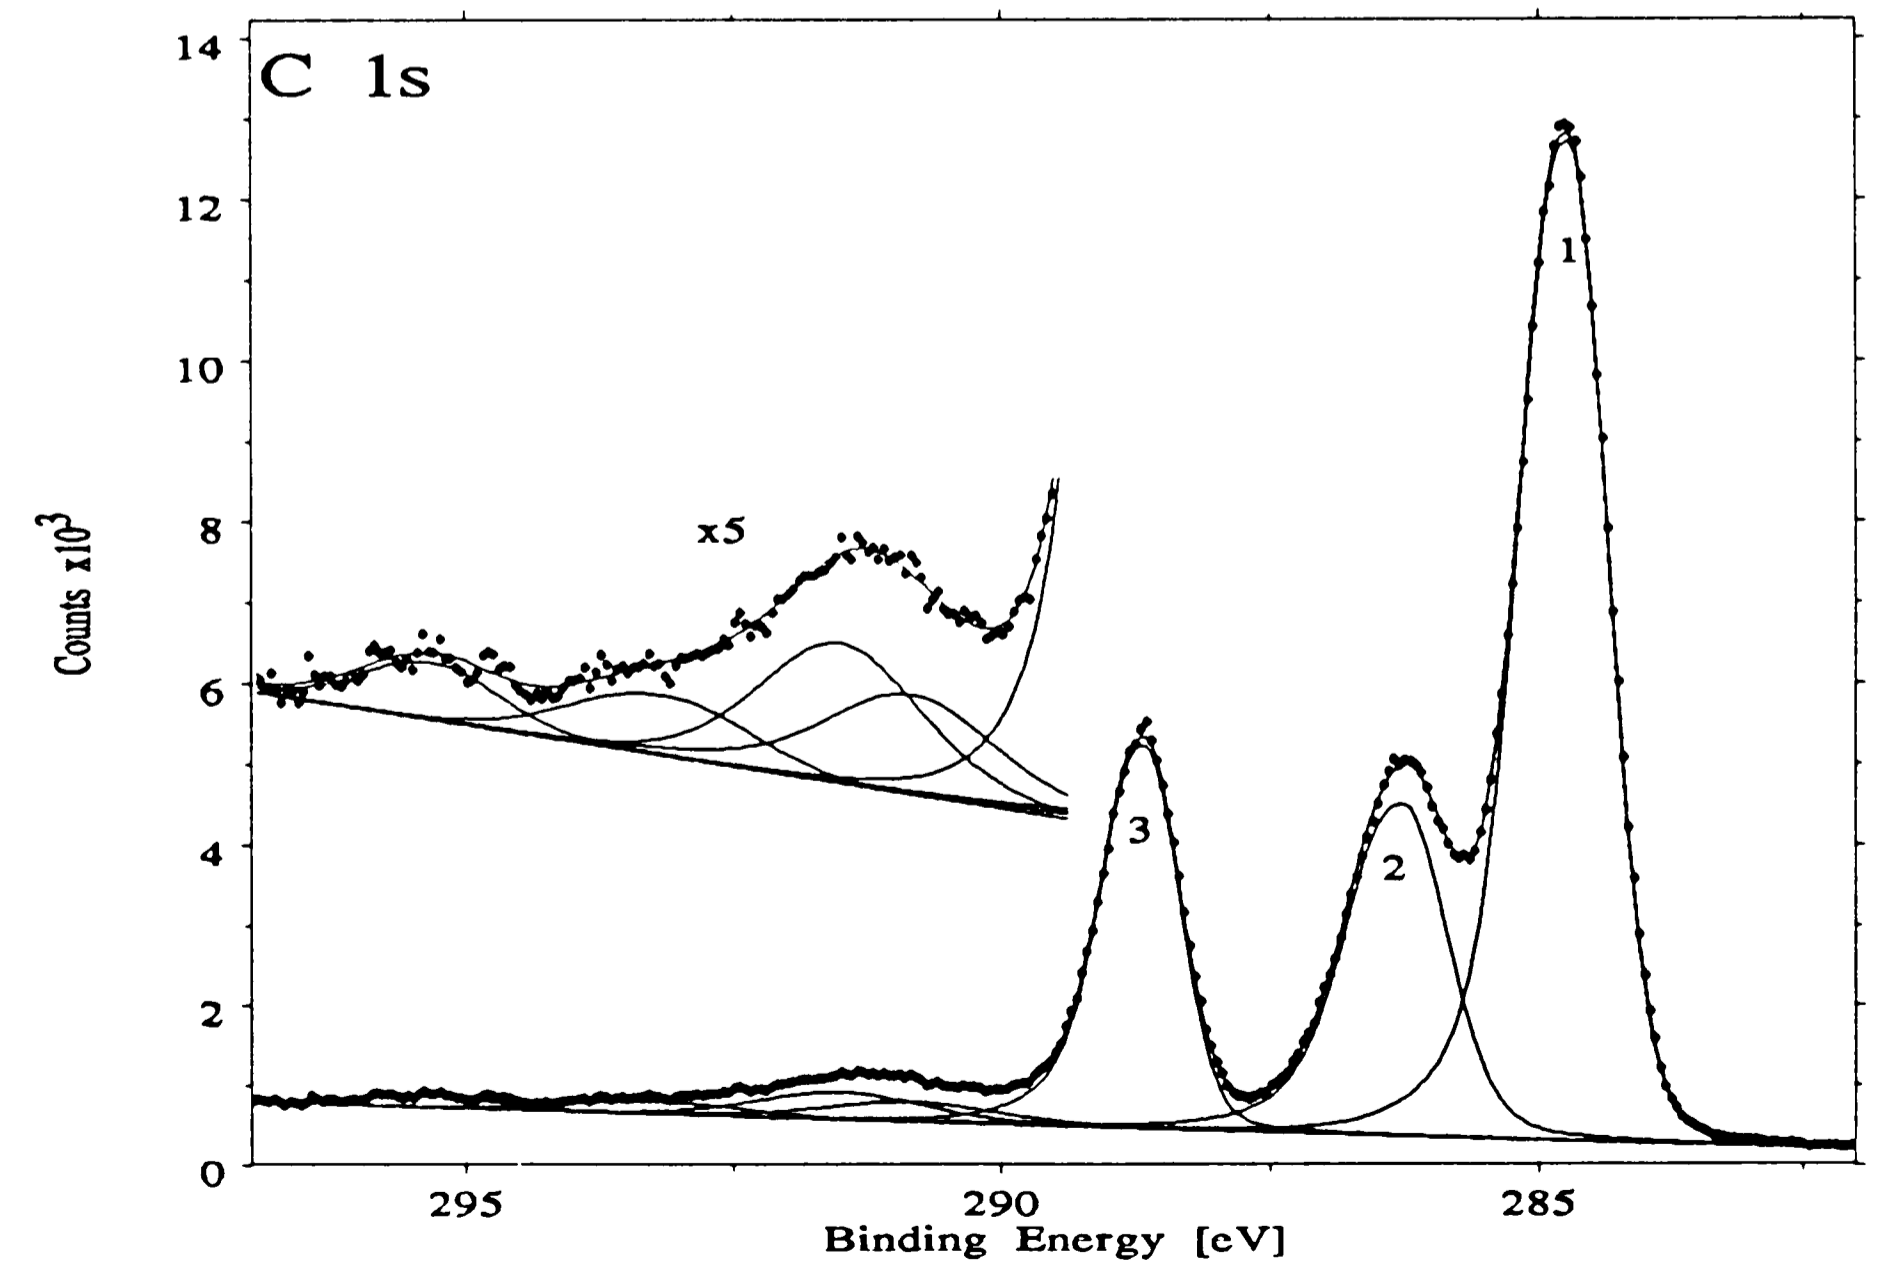

Source: ICI
 Casting solution: (oriented film)
 Degradation index: 0, O/C
 VB acquisition: 2
 Charging reference: aromatic CH = 284.70 eV
 Shake-up: 7% (C 1s), 4% (O 1s)

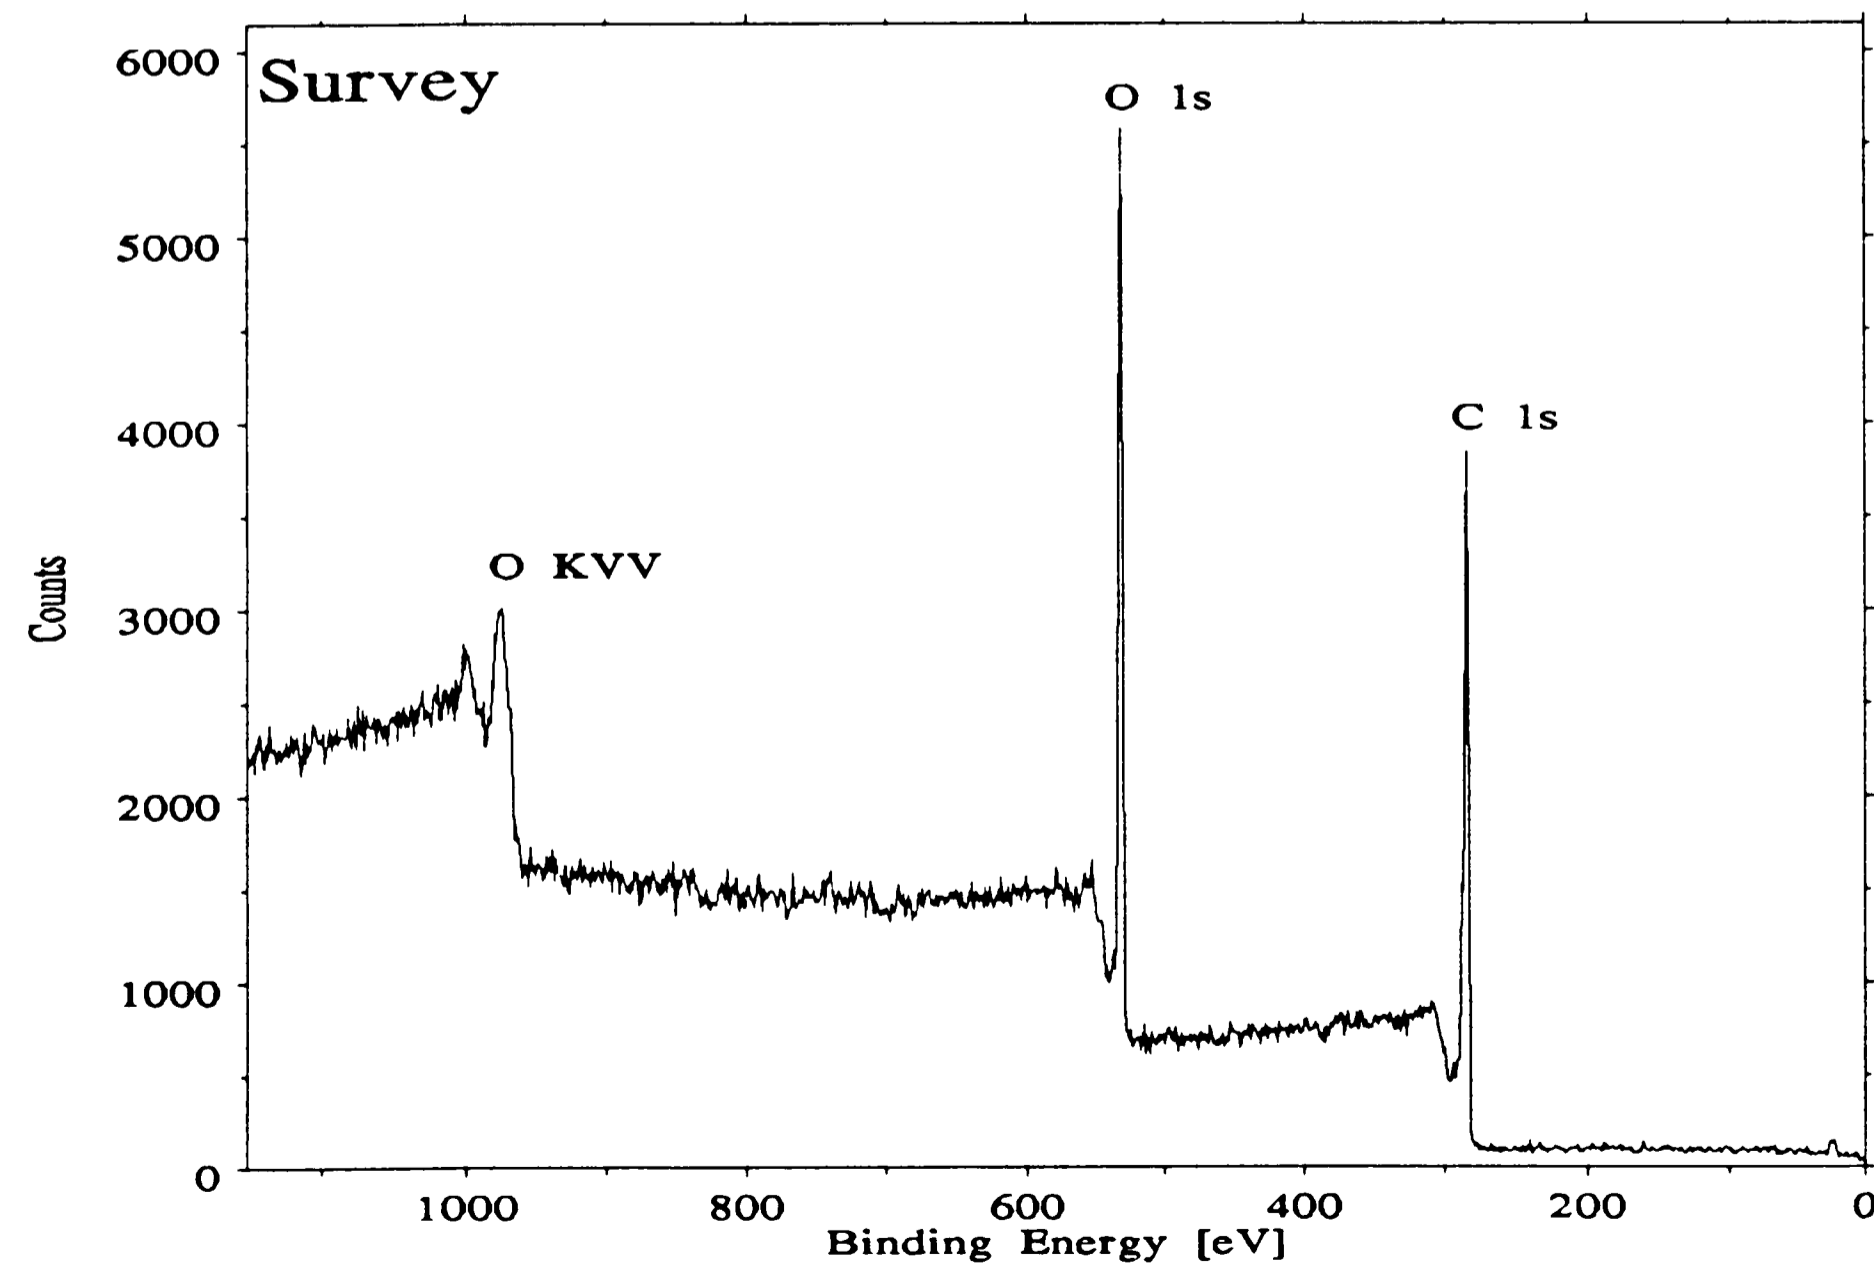

PET

